

## 检测报告

编号: SDHL2005006477FB

日期: 2020-05-26

页码: 第 1 页共 3 页

汉德制造(中国)有限公司  
广州经济技术开发区永和经济区永顺大道摇田河大街 161 号

以下测试之样品是由申请者所提供及确认:

样品名称 : 尚莱狮遮阳面料  
SGS 参考编号 : SDFS2005002715FF\_CN  
到样日期 : 2020-05-15  
检验日期 : 2020-05-15 至 2020-05-26

### 测试结果

序号	测试项目	测试结果	备注
1	GB/T 17591-2006 阻燃织物 一条款 5.1 装饰用织物的燃烧性能试验	见下页	/

详细测试结果请看附页

通标标准技术服务有限公司  
顺德分公司  
授权代表签署



孟军  
批准签署人  
此报告结果仅对测试样品负责



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTC Standards Technical Services Co., Ltd.  
Shunde Branch Harbin

1/F, 1<sup>st</sup> Building European Industrial Park, No.1 Shunde South Road, Wusha Section, Daliang Town, Shunde, Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn  
中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 e sgs.china@sgs.com

## 检测报告

编号: SDHL2005006477FB

日期: 2020-05-26

页码: 第 2 页共 3 页

### 测试依据:

本测试按照 GB/T 17591-2006 阻燃织物 一条款 5.1 装饰用织物的燃烧性能试验; 试验方法按 GB/T 5455-2014 执行。

### I 样品描述

名称	织物
样品克重	457 g/m <sup>2</sup>

### II 测试条件

		标准要求条件	实际环境
预处理环境	温度	(20±2)°C	(20±2)°C
	相对湿度	(65±3)%	(65±3)%
	周期	8~24h	24h
测试环境	温度	15°C~30°C	27.4°C
	相对湿度	30%~80%	65%
重锤的重量	340.2 g	选用的测试气体	丁烷
水洗条件	不水洗, 根据客户要求		

### III 燃烧性能要求

产品类别	项目	考核指标		试验方法
		B <sub>1</sub> 级	B <sub>2</sub> 级	
装饰用织物	损毁长度/mm ≤	150	200	GB/T 5455-2014
	续燃时间/s ≤	5	15	
	阴燃时间/s ≤	5	15	

### IV 测试结果

试样号	经向				
	续燃时间 (s)	阴燃时间 (s)	损毁长度 (mm)	是否有融滴产生	脱脂棉是否被引燃
1	2	0	121	否	否
2	2	0	117	否	否
3	1	0	130	否	否
4	2	0	122	否	否
5	2	0	115	否	否
平均值	2	0	121	---	---



SGS-CSTC (Shunde) Inspection & Testing Services Co., Ltd.  
Shunde Branch Harbin

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.


Attention: To check the authenticity of testing / inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1/F, 1<sup>st</sup> Building European Industrial Park, No.1 Shunde South Road, Wusha Section, Daliang Town, Shunde, Foshan, Guangdong, China 528333 t (86-757)22805888 f (86-757)22805858 www.sgs.com.cn  
中国·广东·佛山市顺德区大良街道办事处五沙顺和南路1号欧洲工业园一号厂房首层 邮编: 528333 t (86-757)22805888 f (86-757)22805858 e sgs.china@sgs.com

试样号	纬向				
	续燃时间 (s)	阴燃时间 (s)	损毁长度 (mm)	是否有融滴产生	脱脂棉是否被引燃
1	2	0	127	否	否
2	1	0	124	否	否
3	4	0	118	否	否
4	2	0	115	否	否
5	2	0	128	否	否
平均值	2	0	122	---	---

V 结论: 该样品符合 GB/T 17591-2006 阻燃织物: 条款 5.1 装饰用织物的燃烧性能试验 B<sub>1</sub> 级要求。

样品照片:

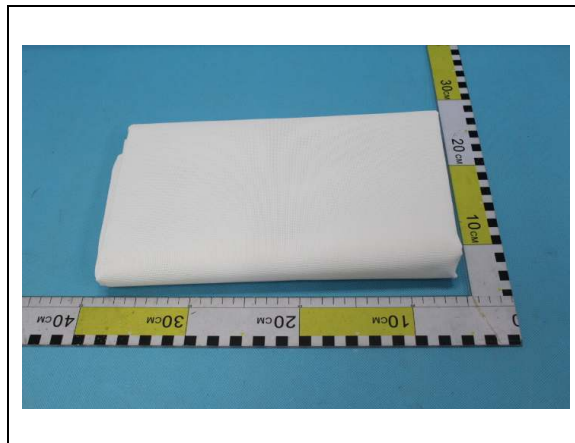

备注: 检测报告仅用于客户科研、教学、内部质量控制、产品研发等目的, 仅供内部参考。

\*\*\*报告结束\*\*\*

